

An Artificial Neural Network Approach to Prediction of Surface Roughness and Material Removal Rate in CNC Turning of C40 Steel

Saadat Ali Rizvi*¹ & Wajahat Ali²

Received 21 November 2020; Revised 15 February 2021; Accepted 16 August 2021;
© Iran University of Science and Technology 2021

ABSTRACT

The present study is focused to investigate the effect of the various machining input parameters such as cutting speed (v_c), feed rate (f), depth of cut, and nose radius (r) on output i.e. surface roughness (R_a and R_q) and metal removal rate (MRR) of the C40 steel by application of an artificial neural network (ANN) method. ANN is a soft computing tool, widely used to predict, optimize the process parameters. In the ANN tool, with the help of MATLAB, the training of the neural networks has been done to gain the optimum solution. A model was established between the computer numerical control (CNC) turning parameters and experimentally obtained data using ANN and it was observed from the result that the predicted data and measured data are moderately closer, which reveals that the developed model can be successfully applied to predict the surface roughness and material removal rate (MRR) in the turning operation of a C40 steel bar and it was also observed that lower the value of surface roughness (R_a and R_q) is achieved at the cutting speed of 800 rpm with a feed rate of 0.1 mm/rev, a depth of cut of 2 mm and a nose radius of 0.4 mm.

KEYWORDS: Modelling; Artificial neural network (ANN); Turning; surface roughness; MRR.

1. Introduction

The basic essential requirement of a customer is the surface quality of a component, which is responsible for the performance of the product and often surface quality is expressed as surface roughness. The surface roughness (R_a) significantly influences the functional performance of mechanical parts such as fatigue strength, wear resistance, and corrosion resistance. surface roughness is influenced by several parameters such as cutting speed, feed, nose radius, depth of cut (doc), tool material, and cutting fluid [1] etc. C40 alloy steel is widely used in industries such as oil and gas pipelines, chemical industries, power plant industries, heat

exchangers etc. due to its easy availability, good machinability, and good weldability properties. Unique characteristics of C 40 steel, it does not lose its ductility when heat treated. In recent years, several mathematical studies based on artificial neural network (ANN) have been carried out because of its good predictive ability i.e. reduces the effort, save money, and time for optimal and efficient implementation of any method [2-4]. Yogesh V. Deshpande et al [5] applied the ANN approach to forecast the surface integrity (roughness) of Inconel 718 material during turning operation and they found that the models developed by an artificial neural network to predicting surface roughness having 98% accuracy. S.C. Cagan et al [6] optimized the process parameters of AZ91D magnesium alloy bars in machining operation by artificial neural network technique and they concluded that the usage of ANN models provides for time and cost-saving in experimental studies. Abdullah et al. [7] studied the ANN approach and Taguchi

* Corresponding author: Saadat Ali Rizvi
sarizvi1@jmi.ac.in

1. Faculty member, University Polytechnic, Jamia Millia Islamia, New Delhi, India.
2. Department of Mechanical Engineering, SCRIET (CCS University), Meerut, India.

technique to determine the surface roughness in the turning process of AISI 4140 steel and it is revealed from their result that neural networks is more effective than predictive regression analysis (Taguchi). Hasan Basri Ulas and Murat Tolga Ozkan[8] compared the ANN results and experimental results of surface roughness and cutting forces of AISI 304, AISI 420, and AISI 2205 material during the turning operation and they concluded that cutting force has been modelled using the ANN technique and ANN results have been found very near closer to the experimental results. T. Deepan Bharathi Kannan et al [9] developed an ANN model for drilling process parameters and they compared the predicted value and measured value and it was observed that both predicted value and measured value were fairly closer. Farag Abdallah et al [10] generated an ANN model to predict the surface roughness and cutting tool temperature during hard machining of C45 alloy steel and they concluded that on increasing the rotational speed and feed rate surface roughness decreases and it was also revealed that the ANN model having a reasonable agreement with the experimental results. Farid Boukezzi et al [11] developed an artificial neural network (ANN) model to predict the roughness of C38 steel during the turning process with P20 carbide insert in dry condition and they concluded that the ANN approach is very suitable to predict the relation between predicted and measured value with accuracy. Kuldip Singh Sangwan et al [12] coupled the ANN technique with the Genetic Algorithm (GA) approach to determine the optimal machining

variable lead to minimum surface roughness during turning of Ti-6Al-4V titanium alloy and they informed that predicted results by ANN designate a good agreement between the predicted values and experimental values. Abderrahmen Zerti et al [13] used RSM approach and ANN models to predict the surface roughness of AISI 420 MSS during the machining operation and they informed that Surface roughness is strongly affected by the feed rate (f) and they also observe that artificial neural network (ANN) model shows better accuracy. Based on the previous literature of studies it is revealed that artificial neural network (ANN) predicted values are very near to the experimental values and indicate that the developed model can be significantly applied to predict the material removal rate (MRR) and surface roughness (SR) [14-16] and it is also observed that surface roughness and material removal rate is highly influenced by feed rate, slightly influenced by the depth of cut (doc) and nose radius of insert [17-18].

2. Material and Method

The workpiece material used in this experiment work is C40 steel. C40 is medium carbon steel with good tensile strength and is extensively used for various industrial applications such as shafts, gear, bolts etc. It is a well-known material that can be easily machined in any condition. The chemical composition and mechanical properties of workpiece material are listed in Tables 1 and 2 respectively.

Tab. 1. Chemical composition of C40 steel

| C | Si | Mn | P | S | Fe | Ni | Mo |
|------|------|------|-------|------|---------|----|----|
| 0.35 | 0.21 | 0.78 | 0.035 | 0.05 | Balance | - | - |

Tab. 2. Mechanical properties of C40 steel

| Material | Yield strength (MPa) | Tensile strength (MPa) | % elongation | Toughness (J) |
|----------|----------------------|------------------------|--------------|---------------|
| C40 | 440 | 610 | 25 | 30 |

2.1. Experimental work

In this research article, C40 steel is used for turning purposes. Machining operation was performed on CNC lathe machine of MIDAS 8i of Fanuc controller of 7.5 KW powers of spindle and spindle speed of machine varies from 40-4000 rpm, with CNMG type tungsten coated carbide tool insert. The insert was fixed on a

right-hand tool holder. Experimental was used in this process is shown in fig.1. after completing machining process, the roughness (R_a , R_q) of all twenty-seven (27) machined workpieces was measured with portable surface roughness tester (make: Surtronic 3+, Japan). Surface roughness was measured at three points along the circumference of workpiece. Table 3 enlists the

machining process parameters and their levels used in this experiment.

Tab. 3. Process Parameters

| Parameters | Unit | Level-I | Level-II | Level-III |
|---------------|--------|---------|----------|-----------|
| Cutting speed | rpm | 400 | 600 | 800 |
| feed | mm/rev | 0.1 | 0.2 | 0.3 |
| Depth of cut | mm | 0.7 | 1.6 | 2.0 |
| Nose radius | mm | 0.4 | 0.8 | 1.2 |

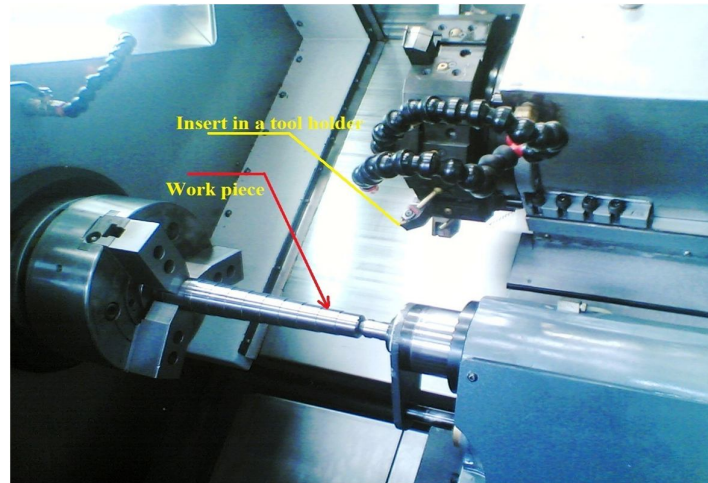


Fig.1. Experimental setup of CNC turning

The experiments were performed with values of cutting speed from 400 to 800 rpm, feed rate from 0.1 to 0.3 mm/rev, depth of cut from 0.7 to 2.0 mm, and nose radius 0.4-1.2 mm. Table 4 shows the experimental result carried out in this

experiment. In this experimental work, the Taguchi technique was applied to optimize the process parameters and L_{27} orthogonal arrays DOE was used.

Tab. 4. Experimental result

| Trial No | cutting speed | Feed | DOC | NR | R_a | | R_q | | MRR | |
|----------|---------------|------|-----|-----|--------------|-----------|--------------|-----------|--------------|-----------|
| | | | | | Experimental | Predicted | Experimental | Predicted | Experimental | Predicted |
| 1 | 400 | 0.1 | 0.7 | 0.4 | 3.72 | 3.885 | 4.89 | 4.965 | 389 | 529.053 |
| 2 | 400 | 0.1 | 1.6 | 0.8 | 3.52 | 3.551 | 4.75 | 4.615 | 765 | 765.741 |
| 3 | 400 | 0.1 | 2 | 1.2 | 3.02 | 3.146 | 4.13 | 4.277 | 1120 | 918.013 |
| 4 | 400 | 0.2 | 0.7 | 0.4 | 4.3 | 4.392 | 5.36 | 5.029 | 431 | 1352.270 |
| 5 | 400 | 0.2 | 1.6 | 0.8 | 5.66 | 5.279 | 6.81 | 6.348 | 880 | 444.591 |
| 6 | 400 | 0.2 | 2 | 1.2 | 3.02 | 3.217 | 4.25 | 4.331 | 1323 | 1323.459 |
| 7 | 400 | 0.3 | 0.7 | 0.4 | 9.02 | 9.123 | 10.45 | 10.78 | 495 | 495.647 |
| 8 | 400 | 0.3 | 1.6 | 0.8 | 3.06 | 3.102 | 4.23 | 4.322 | 1052 | 1055.319 |
| 9 | 400 | 0.3 | 2 | 1.2 | 2.5 | 2.537 | 3.67 | 3.35 | 1511 | 1601.498 |
| 10 | 600 | 0.2 | 0.7 | 1.2 | 6.82 | 6.553 | 7.91 | 7.117 | 1682 | 1683.167 |
| 11 | 600 | 0.2 | 1.6 | 0.4 | 3.2 | 2.909 | 4.33 | 3.985 | 523 | 395.422 |
| 12 | 600 | 0.2 | 2 | 0.8 | 4 | 3.808 | 5.17 | 4.996 | 1077 | 1075.387 |
| 13 | 600 | 0.3 | 0.7 | 1.2 | 4.62 | 4.882 | 5.79 | 5.693 | 2061 | 2061.297 |
| 14 | 600 | 0.3 | 1.6 | 0.4 | 6.36 | 5.944 | 7.42 | 7.96 | 686 | 685.201 |
| 15 | 600 | 0.3 | 2 | 0.8 | 3.86 | 4.111 | 4.95 | 5.279 | 1386 | 1620.611 |
| 16 | 600 | 0.1 | 0.7 | 1.2 | 2.94 | 3.826 | 4.11 | 4.169 | 2387 | 2387.490 |
| 17 | 600 | 0.1 | 1.6 | 0.4 | 2.02 | 1.953 | 3.15 | 3.226 | 792 | 791.850 |
| 18 | 600 | 0.1 | 2 | 0.8 | 3.74 | 3.792 | 4.98 | 4.784 | 1588 | 1587.082 |
| 19 | 800 | 0.3 | 0.7 | 0.8 | 2.68 | 2.858 | 3.81 | 3.775 | 1805 | 1804.078 |

| | | | | | | | | | | |
|----|-----|-----|-----|-----|------|-------|------|-------|------|----------|
| 20 | 800 | 0.3 | 1.6 | 1.2 | 3.46 | 3.13 | 4.86 | 5.053 | 2739 | 2736.296 |
| 21 | 800 | 0.3 | 2 | 0.4 | 7.1 | 6.95 | 8.54 | 8.825 | 911 | 910.439 |
| 22 | 800 | 0.1 | 0.7 | 0.8 | 2.68 | 2.51 | 3.72 | 3.527 | 2021 | 2017.238 |
| 23 | 800 | 0.1 | 1.6 | 1.2 | 3.3 | 3.677 | 4.56 | 4.847 | 3269 | 3532.181 |
| 24 | 800 | 0.1 | 2 | 0.4 | 1.16 | 1.194 | 2.36 | 2.906 | 1023 | 1024.876 |
| 25 | 800 | 0.2 | 0.7 | 0.8 | 2.04 | 2.207 | 3.16 | 2.923 | 2351 | 2350.715 |
| 26 | 800 | 0.2 | 1.6 | 1.2 | 4.86 | 4.548 | 5.99 | 5.358 | 3583 | 3581.569 |
| 27 | 800 | 0.2 | 2 | 0.4 | 3.38 | 3.332 | 4.74 | 4.481 | 1120 | 1119.929 |

3. Result and Discussion

3.1. Artificial neural network (ANN)

An artificial neural network (ANN) is a mathematical or computational model which is stimulated by biological neurons functional aspects like brain aspect [19]. A neuron is a primary element of the neural network, which is composed of neurons, input, weights, activation function, summation function, and output. The mathematical formula for calculating the net input of the neuron is given by the equation (1) where as equation (2) is used to compute the activation function.

$$NET_i = \sum_{j=1}^n w_{ij}x_j + w_{bi} \quad (1)$$

Where NET_i =weighted sum of the input to the i^{th} processing element

w_{ij} =weight of the connections between the i^{th} processing elements

x_j =output of the j^{th} processing element

w_{bi} =weight of the biases between the layers

n =number of processing elements in the previous layer

$$f(NET_i) = \frac{1}{(1 + e^{-NET_i})} \quad (2)$$

An ANN model was developed by the NN tool of MATLAB software. MATLAB 2017a was used to generate the model. ANN neurons structure containing input, hidden layer, and output layer as shown in fig 2 and fig 4 shows improved an ANN model using MATLAB software.

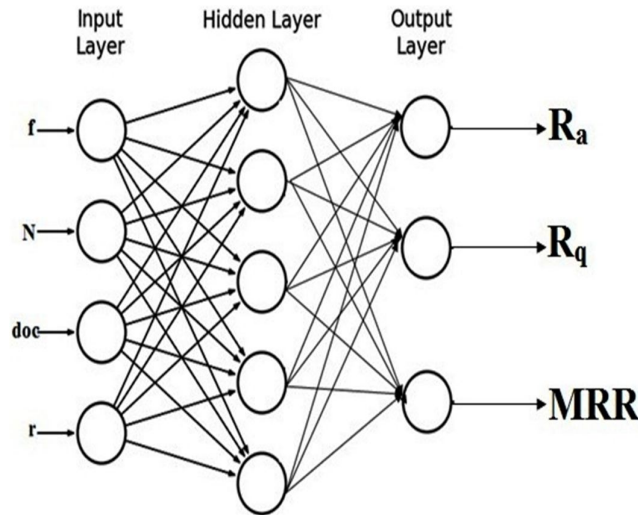


Fig. 2. ANN structure (4-14-3)

The simulated multi-layer ANN structure consists of four neurons in the input layer i.e. feed rate (f), cutting speed (v), depth of cut, and nose radius (r). Three neurons in the output layer represent R_a , R_q and MRR . One hidden layer with 14 neurons was applied between the input layer and output layer as shown in fig 2. In this training

process, the artificial neural network structure is set like 4-14-3, i.e. four inputs, one hidden layer (14 neurons), and three put as shown in fig 3. The trial and error method was selected to execute the algorithm which is linked the neuron to recognize the hidden layer and allocate the neuron for all

hidden layers. The Artificial Neural Network (ANN) model generated is expressed in fig.3.

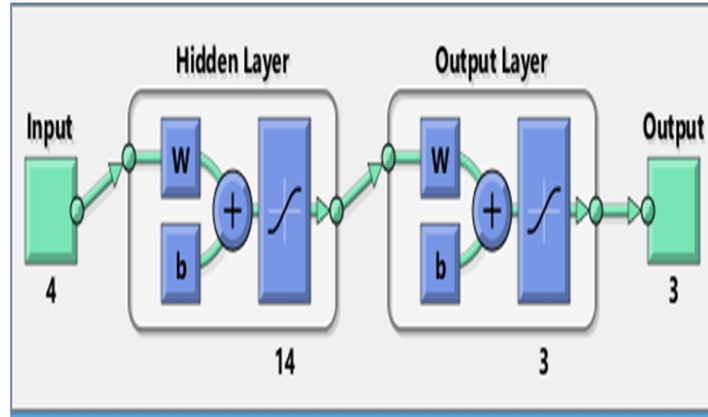


Fig. 3. Artificial neural network (ANN) model




Fig. 4. improved ANN model by MATLAB R2017a

The number of neurons in the first hidden layer was selected by trial and error. Analysis of the graphical functions is demonstrated in fig 5 & fig

6 respectively. Fig 5 & fig 6 shows that the MLP 4-14-3 configuration had the minimum error in the validation set.

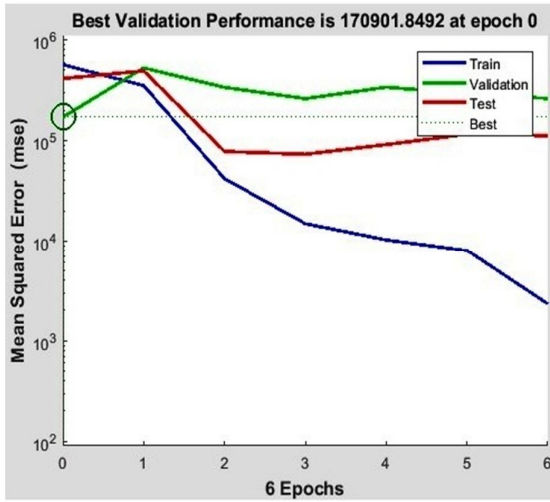


Fig. 5. Best validation of ANN

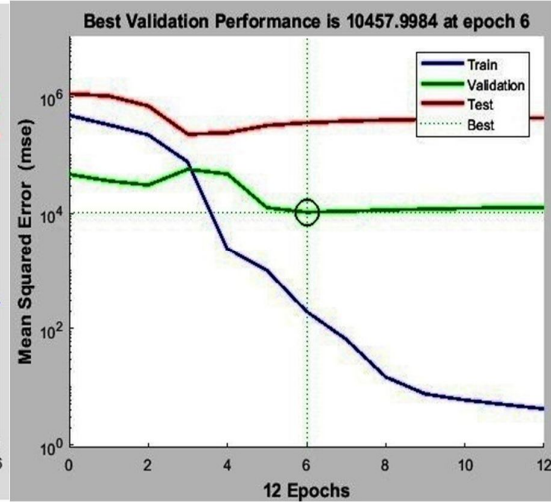


Fig. 6. Best validation of ANN

The performance curve of ANN i.e. regression curve for all patterns, training, validation and testing are summarised in fig.7. For surface roughness (R_a , R_q) and MRR respectively. For a perfect fit, the data should fall along a 45° line (dash line) as shown in fig 7. The dotted line in fig 7 indicates the best line fit whereas the solid line indicated the perfect fit. The regression

coefficient for training and validation was noted at 0.99987 and 0.96555 respectively, which is very closer to 1. As the value of the testing coefficient is 1, which shows that the trained model is best fitted for testing the data and it is also observed that prediction is relatively accurate as surface roughness predicted point lie very near to the experimental values [20].

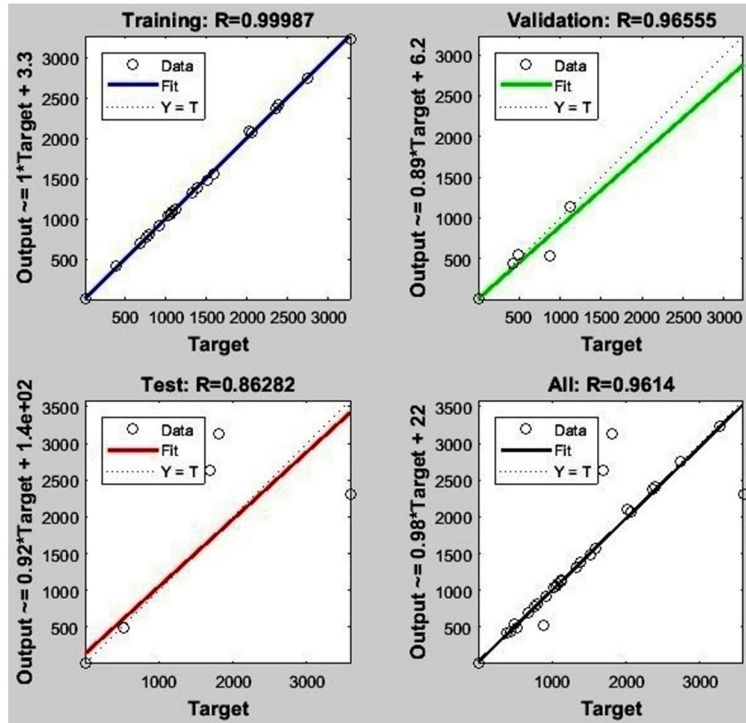


Fig. 7. Network model regression analysis for a. training dataset, b. validation dataset, c. testing dataset and d. combined datasets.

Compression of experimental data and predicted data of three out for twenty seven (27) experiments are listed in fig 8 and fig 9

respectively. Fig. 8 show the surface roughness R_a and R_q values and from figure it was observed that there is a good agreement between predicted

data and experimental data. Results of this study validates with the previous work [21] as the

graph of surface roughness almost is same.

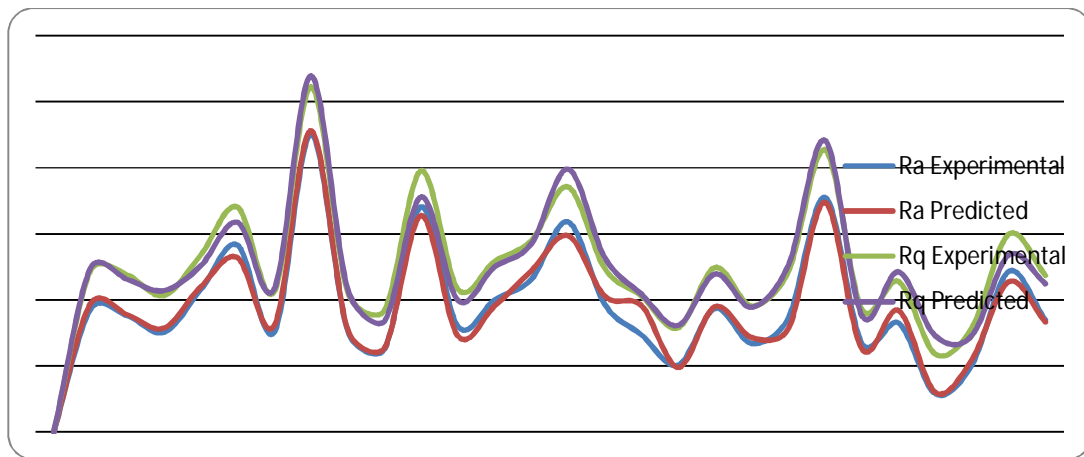


Fig. 8. comparison of experimental and estimated surface roughness (R_a and R_q)

Fig. 9 showed the results of prediction and actual data for the material removal rate of the machined parts. However, the deviation at run 3 and 4 were observed. Fig 9 depicts that error is within the limit, and hence ANN technique can

be effectively applied to predict the MRR and the pattern of the graph is like the horn of bovine [22-23]. However, the accuracy of the MRR prediction is within acceptable range. There for, it can be suggested that model is acceptable.

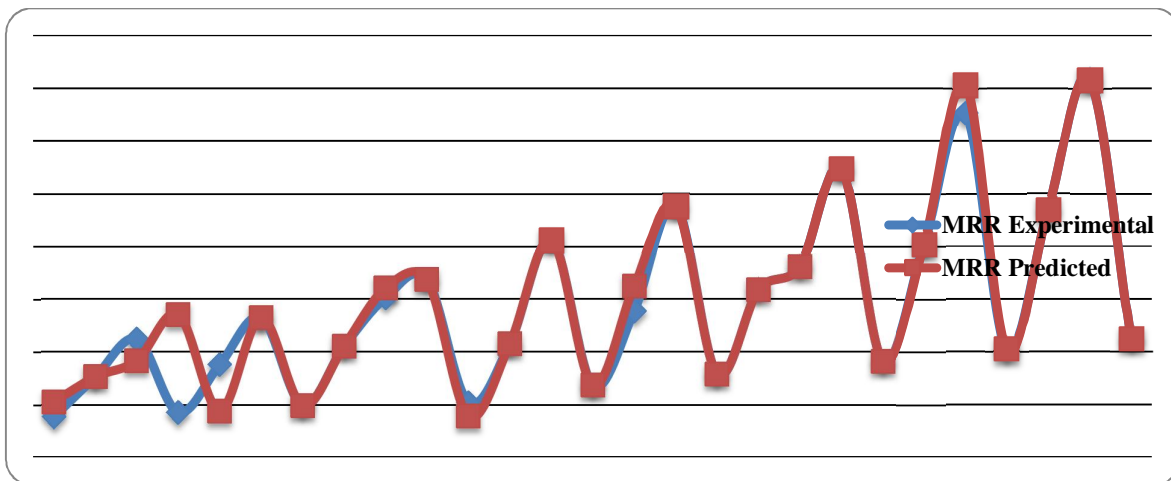


Fig. 9. comparison of experimental and estimated material removal rate (MRR)

4. Conclusion

Based on the theoretical knowledge and practical experience with ANN approach, development and training, authors have been observed that ANN approach can be applied to predict the surface roughness and MRR and from the present study, the following important conclusions have been drawn

1) An ANN model of 4-14-3 structure, found best suitable for this study.

- 2) An ANN model has been designed to predict the surface roughness and MRR in turning of C40 steel.
- 3) Lower the value of surface roughness (R_a and R_q) is achieved at the cutting speed of 800 rpm with a feed rate of 0.1 mm/rev, a depth of cut of 2 mm and a nose radius of 0.4 mm.
- 4) Higher rate of material removal rate is achieved at the cutting speed of 800 rpm with a feed rate of 0.2 mm/rev, a depth of

cut of 1.6 mm and a nose radius of 1.2 mm.

- 5) From result it was also observed that there is an excellent agreement between the two patterns i.e. experimental and predicted value hence the ANN model is a very reliable model to predict the surface roughness and material removal rate (MRR).

References

- [1] Saadat Ali Rizvi, Wajahat Ali, Manufacturing Science-II, S.K. Kataria & Sons Publisher, Delhi, (2010), p. 87.
- [2] Karkalos NE, Galanis NI, Markopoulos AP, Surface roughness prediction for the milling of Ti–6Al–4V ELI alloy with the use of statistical and soft computing techniques, *Measurement*, Vol. 90, (2016), pp. 25-35.
DOI:10.1016/j.measurement.2016.04.039.
- [3] D. Rajeev, D. Dinakaran, S.C.E. Singh, “Artificial neural network based tool wear estimation on dry hard turning processes of AISI4140 steel using coated carbide tool”, *Bull. Pol.Ac.: Tech.* Vol. 65, No. 4, (2017), pp. 553-559.
DOI: 10.1515/bpasts-2017-0060.
- [4] Mahmood khani, Y.;Wells, M.A.; Song, G., Prediction of roll force in skin pass rolling using numerical and artificial neural network methods, *Ironmak. Steelmak.* Vol. 44, (2017), pp. 281-286.
DOI: 10.1080/03019233.2016.1210405.
- [5] Yogesh V. Deshpande,Atul B. Andhare,Pramod M. Padole, Application of ANN to estimate surface roughness using cutting parameters, force, sound and vibration in turning of Inconel 718, *SN Applied Sciences*, Vol. 1, (2019), p. 104.
DOI:10.1007/s42452-018-0098-4.
- [6] S.C. Cagan,M. Aci, B.B. Buldumc,C. Aci, Artificial neural networks in mechanical surface enhancement technique for the prediction of surface roughness and microhardness of magnesium alloy, *Bulletin of the Polish Academy of Sciences Technical Sciences*, Vol. 67, No. 4, (2019).
DOI: 10.24425/bpasts.2019.130182.
- [7] A.A. Abdullah, U.J. Naeem, C.H. Xiong, Estimation and optimization cutting conditions of surface roughness in hard turning using Taguchi approach and artificial neural network, *advanced Materials Research, Trans Tech Publ.*, (2012), pp. 662-668.
DOI: 10.4028/ www.scientific.net/AMR.463-464.662.
- [8] Hasan Basri Ulas,Murat Tolga Ozkan, Turning process investigation of materials austenitic,martensitic and duplex steel Prediction of cutting forces using Artificial Neural Network (ANN) techniques, *Indian Journal of Engineering & Material Sciences*, Vol. 26, No. 2, (2019), pp. 93-104,
DOI:10.18280/jesa.520211.
- [9] T. Deepan Bharathi Kannan, B. Suresh Kumar, G. Rajesh Kannan, M. Umar, Mohammad Chand Khan, Application of Genetic Algorithm Technique for Machining Parameters Optimization in Drilling of Stainless Steel, *Mechanics and Mechanical Engineering* Vol. 23, (2019), pp. 271-276.
DOI: 10.2478/mme-2019-0036.
- [10] Farag Abdallah, Sabreen A. Abdelwahab, Yasser Fatouh, Ibrahim Ahmed, Modeling and Simulation of Cutting Tool Temperature in Turning Process of C45 Alloy Steel using Artificial Neural Network (ANN), *International Research Journal of Engineering and Technology (IRJET)*, Vol. 6, No. 1, (2019), pp. 518-525.
- [11] Farid Boukezzi, Rachid Nouredine, Ali Benamar, Farid Nouredine, Modelling, prediction and analysis of surface roughness in turning process with carbide tool when cutting steel C38 using artificial neural network, *International Journal of Industrial and Systems Engineering, Inderscience*, Vol. 26, No. 4, (2017), pp. 567-583.
DOI: 10.1504/IJISE.2017.10005302.

- [12] Kuldip Singh Sangwan, Sachin Saxena, Girish Kant, Optimization of Machining Parameters to Minimize Surface Roughness using Integrated ANN-GA Approach, *Procedia CIRP* Vol. 29, (2015), pp. 305-310.
DOI: 10.1016/j.procir.2015.02.002.
- [13] Abderrahmen Zerti , Mohamed Athmane Yaltese, Oussama Zerti , Mourad Nouioua, Riad Khettabi, Prediction of machining performance using RSM and ANN models in hard turning of martensitic stainless steel AISI 420, *Proc IMechE Part C: J Mechanical Engineering Science*, (2019), pp. 1-24.
DOI: 10.1177/0954406218820557.
- [14] M. Vishnu Vardhan, G.Sankaraiah, M.Yohan, Prediction of Surface roughness & Material Removal Rate for machining of P20 Steel in CNC milling using Artificial Neural Networks, *Materials Today: Proceedings* Vol. 5, (2018), pp. 18376-18382.
DOI: 10.1016/j.matpr.2018.09.010.
- [15] Abhishek Srivastava, Adarsh Sharma, Aditya Singh Gaur, Rahul, Yashwant kumar Modi, prediction of surface roughness for CNC turning of EN8 Steel bar using Artificial Neural Network model, *Journal Europeen des systems Automatisees*, Vol. 52, No. 2, (2019), pp. 185-188.
DOI: 10.18280/jesa.52011.
- [16] T. Y. Wu, K. W. Lei, Prediction of surface roughness in milling process using vibration signal analysis and artificial neural network, *International Journal of Advanced Manufacturing Technology*, Vol. 102, No. 315, (2019).
DOI: 10.1007/s00170-018-3176-2.
- [17] Ahmed A. Elsadek, Ahmed M. Gaafer ,S.S. Mohamed, Surface roughness prediction in hard-turning with ANN and RSM, *Journal of the Egyptian Society of Tribology*, Vol. 17, No. 2, (2020), pp. 13-22.
DOI: 10.21608/jest.2020.81079.
- [18] S.K Thangarasu, S.Shankar, T.Mohanraj, K.Devendran, Tool wear prediction in hard turning of EN8 steel using cutting force and surface roughness with artificial neural network, *Proc IMechE Part C:J Mechanical Engineering Science*, pp. 1-14,
DOI: 10.1177/0954406219873932.
- [19] A. Yeganefar, S. A. Niknam, and R. Asadi, The use of support vector machine, neural network, and regression analysis to predict and optimize surface roughness and cutting forces in milling, *International Journal of Advanced Manufacturing Technology*, Vol. 105, Nos. 1-4, (2019), pp. 951-965.
DOI: 10.1007/s00170-019-04227-7.
- [20] Jafarian, F., Taghipour, M, Amirabadi, H., Application of artificial neural network and optimization algorithms for optimizing surface roughness, tool life and cutting forces in turning operation. *J. Mech.Sci. Technol.* Vol. 27, (2013), pp. 1469-1477.
DOI: 10.1007/s12206-013-0327-0.
- [21] Mirko Ficko , Derzija Begic-Hajdarevic , Maida Cohodar Husic , Lucijano Berus , Ahmet Cekic, Simon Klancnik, Prediction of Surface Roughness of an Abrasive Water Jet cut using an Artificial Neural Network, *Materials* Vol. 14, (2021), p. 3108.
DOI: 10.3390/ma14113108.
- [22] Mohammad Arafat, Teddy Sjafrizal, Rino Andias Anugraha, An artificial neural network approach to predict energy consumption and surface roughness of a natural material, *SN Applied Sciences* Vol. 2, (2020), p. 1174.
DOI: 10.1007/s42452-020-2987-6.
- [23] Samya Dahbi, Latifa Ezzine, Haj EL Moussami, Modeling of cutting performances in turning process using artificial neural networks, *International Journal of Engineering Business Management*, Vol. 9, (2017), pp. 1-13.
DOI: 10.1177/1847979017718988.

Follow This Article at The Following Site:

RIZVI S A, Ali W. An artificial neural network approach to prediction of surface roughness and material removal rate in CNC turning of C40 steel. IJIEPR. 2021; 32 (3) :1-10
URL: <http://ijiepr.iust.ac.ir/article-1-1163-en.html>

